

Modification of the classical Heisenberg helimagnet by weak uniaxial anisotropy and magnetic field

I. A. Zaliznyak

P. L. Kapitza Institute for Physical Problems, ul. Kosygina 2, 117334 Moscow, Russia

M. E. Zhitomirsky

*L. D. Landau Institute for Theoretical Physics, ul. Kosygina 2, 117334 Moscow, Russia and
Institute for Solid State Physics, University of Tokyo, Tokyo 106 Japan*

(Dated: February 4, 1995)

Classical ground state of the isotropic Heisenberg spin Hamiltonian on a primitive Bravais lattice is known to be a single- $\mathbf{Q}$ planar spin spiral. A uniaxial anisotropy and external magnetic field distort this structure by generating the higher-order Fourier harmonics at wave-vectors $n\mathbf{Q}$ in the spatial spin configuration. These features are not captured in the formalism based on the Luttinger-Tisza theorem, where the classical ground state energy is minimized under the “weak” condition on the length of the spins. We discuss why the correct solution is lost in that approach and present an alternative microscopic treatment of the problem. It allows to find the classical ground state for general $\mathbf{Q}$ for both easy-axis and easy-plane uniaxial second-order anisotropy, and for any orientation of the magnetic field, by treating the effect of anisotropy (but not the field) as a perturbation to the exchange structure. As a result, the classical ground state energy, the uniform magnetization, and the magnetic Bragg peak intensities that are measured in experiment, are calculated.

PACS numbers: 75.10Hk, 75.25+z, 75.50Ee

I. INTRODUCTION

For more than three decades, helical spin structures have been a subject of intensive studies. Having been discovered theoretically in the pioneering works of Yoshimori¹ and Villain², they were found experimentally in a large variety of materials. Most extensive work was devoted to the investigation and explanation of different ordered phases and phase transitions in the rare-earth metals from Tb to Tm. These phases were shown to result from the intricate distortion of the incommensurate, almost ferromagnetic exchange helimagnet by temperature and strong crystal field anisotropies.^{3,4} However, for the reason discussed below, a classical treatment, finally generalized by Lyons and Kaplan⁵, predicts no such distortion in the ground state of the quasi-isotropic Heisenberg Hamiltonian at $T = 0$.

A simple but nontrivial example of the commensurate spiral is a triangular magnetic ordering found in the hexagonal antiferromagnets of CsNiCl₃ type. Their magnetic structure consists of six sublattices, three in each hexagonal plane at an angle $\approx 120^\circ$ to each other, whereas spins in the adjacent planes are antiparallel. Such compounds have recently attracted much attention because of their pronounced quasi-one-dimensional nature (exchange between the adjacent spins along the hexagonal axis is much stronger than that between the neighbors in the plane). Experiments^{6,7,8} have demonstrated large deviations of the staggered magnetization and susceptibility in these materials from the results of the mean field (MF) calculations which should be valid for classical spins, $S \gg 1$, and thus the importance of quantum fluctuations. Therefore, these are also excellent examples of quantum helimagnets which also have been recently

studied in the literature.^{9,10,11} Chubukov¹² and Tanaka *et al.*¹³ calculated classical spin reorientation process in magnetic field (see also Ref. 14) and the antiferromagnetic resonance spectra in the hexagonal antiferromagnets of CsNiCl₃ type on the basis of six-sublattice model. It appears that even for six sublattices the problem is very difficult to handle in this way, and essentially no explicit analytical results can be obtained for the spin-wave spectrum. Our motivation in the present work was to develop a simpler and more general procedure for finding the classical ground-state spin configurations, which would allow to perform reasonably unsophisticated spin-wave calculations. We adopt the approach similar to that used by Nagamiya³ and Kaplan⁴. Essentially, it is extension of the iterative procedure first suggested by Cooper *et al.*¹⁵ for the easy-plane, almost ferromagnetic spirals, to a general helimagnet. However, keeping in mind its application to the commensurate antiferromagnets, we will neither discuss here the incommensurability effects, nor changes in the ordering wave-vector $\mathbf{Q}$ by the anisotropy and magnetic field that occur for general $\mathbf{Q}$ position. These problems, as well as the incommensurate-commensurate transitions, were treated elsewhere in the framework of the phenomenological approach.^{16,17}

We start from the following spin Hamiltonian, which describes the low-temperature magnetic properties of a large class of crystals where spins of the magnetic ions are localized at lattice sites,

$$\hat{\mathcal{H}} = \sum_{i,j} J_{ij} \mathbf{S}_i \mathbf{S}_j + D \sum_i (S_i^z)^2 - \gamma \mathbf{H} \sum_i \mathbf{S}_i. \quad (1)$$

Here the first term is the Heisenberg exchange interaction, the second term describes the lowest-order uniaxial

anisotropy, and the last term is the Zeeman energy (γ is the gyromagnetic ratio). The anisotropy arises from the magnetic spin-spin and spin-orbit interactions. Hence, the constant D incorporates a small relativistic ratio $(v/c)^2$, where v is the average velocity of the electron in the atom, and c is the velocity of light. This constant is usually considered to be small in comparison with the exchange coupling constants J_{ij} which are of the electrostatic origin. This condition, however, can be violated in the quasi-low-dimensional magnetic materials, where the superexchange path along some directions is indirect and the corresponding constants J_{ij} are very small. Although such cases, as well as singlet ground state systems in which D is intrinsically very large may also be of interest, in the present paper we will always imply condition $|D| \ll |J_{ij}| \neq 0$ fulfilled. We also restrict our attention to the cases in which summation in (1) is performed over a single Bravais lattice with N sites.

In the spin-wave theory, the ground state and the excitation spectrum of quantum Hamiltonian (1) are obtained in a semiclassical approximation, based on $1/S$ expansion. The starting point for such calculation is to find an equilibrium spin configuration with the minimum ground state (GS) energy E_{GS} in the classical limit, $S \rightarrow \infty$. In the case of the isotropic Heisenberg Hamiltonian, a rather complete spin-wave theory describing its low-temperature properties has been developed.^{9,10,11} However, the problem becomes extremely complicated if the anisotropy which exists in real compounds is included together with the magnetic field. In this case, even for classical helimagnets, very little general results were actually obtained. Some particular cases were successfully treated in Refs. 3 and 15, but resulted in rather involved and hardly usable expressions (in part, because an attempt to account for the six-fold anisotropy, in addition to the easy-plane anisotropy, made problem much more complicated). Here we present calculation of the ground state spin configurations for the Hamiltonian (1) for different orientations of the magnetic field, and taking into account the anisotropy (but not the field) as a first-order perturbation of the exchange Hamiltonian.

II. FAILURE OF THE WEAK CONDITION

It is known that ground state of a system of equivalent classical spins on a simple Bravais lattice, in the exchange approximation, is a flat spin spiral described by a wave-vector $\mathbf{Q}$ (this includes ferromagnetism ($\mathbf{Q} = 0$) and antiferromagnetism ($\mathbf{Q} = \mathbf{K}/2$) as particular cases). A rigorous proof of this result is obtained by solving the mathematical problem of finding the absolute minimum of the function (1), which depends on $3N$ classical variables S_i^α , under N conditions,

$$\mathbf{S}_i^2 = S^2, \forall i, \quad (2)$$

imposed on the lengths of the classical spins. This problem is solved by introducing N Lagrange multipliers λ_i .

Switching to the Fourier representation to use the lattice translational symmetry, one obtains the following system of equations for spin configuration which minimizes the Hamiltonian

$$N J_{\mathbf{k}} \mathbf{S}_{\mathbf{k}} + \mathbf{e}_z D S_{\mathbf{k}}^z - \sum_{\mathbf{k}'} \lambda_{\mathbf{k}'} \mathbf{S}_{\mathbf{k}-\mathbf{k}'} = \frac{1}{2} \gamma \mathbf{H} \delta_{\mathbf{k},0},$$

$$\sum_{\mathbf{k}'} \mathbf{S}_{\mathbf{k}'} \mathbf{S}_{\mathbf{k}-\mathbf{k}'} = S^2 \delta_{\mathbf{k},0}. \quad (3)$$

Here $J_{\mathbf{k}}$, $\mathbf{S}_{\mathbf{k}}$, and $\lambda_{\mathbf{k}}$ are the lattice Fourier transforms of the functions J_{ij} , $\mathbf{S}_i$, and λ_i , respectively; $\mathbf{e}_z$ is a unit vector along z direction, and $\delta_{\mathbf{k},0}$ is a three-dimensional Kronecker symbol. From Eq. (3) we easily obtain the classical ground-state energy as

$$\frac{1}{N} E_{GS} = \lambda_0 S^2 - \frac{\gamma}{2} \mathbf{H} \mathbf{S}_0. \quad (4)$$

There are two points to note here. First, Eq. (3) is a complicated inhomogeneous system of nonlinear equations, for which no general solution is easily found. Second, the resultant ground-state energy explicitly depends only on the values of λ_0 and $\mathbf{S}_0$ (on the latter only if $\mathbf{H} \neq 0$), so all $\lambda_{\mathbf{k}}$ for $\mathbf{k} \neq 0$ seem to be irrelevant. This fact encourages one to look for the solution for which the Lagrange multipliers have the form $\lambda_{\mathbf{k}} = \lambda_0 \delta_{\mathbf{k},0}$ and the system is largely linearized. Evidently, such procedure is equivalent to taking into account only one of the N conditions given by the second relation in Eq. (3), or to replacing Eq. (2) by the so-called “weak” condition, $\sum_i \mathbf{S}_i^2 = N S^2$. This standard approach was formalized by Lyons and Kaplan⁵. Then, the solution is easily found in the form of a single- $\mathbf{Q}$ spiral,

$$\mathbf{S}_{\mathbf{k}} = \mathbf{S}_0 \delta_{\mathbf{k},0} + \mathbf{S}_{\mathbf{Q}} \delta_{\mathbf{k},\mathbf{Q}} + \mathbf{S}_{-\mathbf{Q}}^* \delta_{\mathbf{k},-\mathbf{Q}},$$

$$\lambda_0 = N J_{\mathbf{Q}} = N \min\{J_{\mathbf{k}}\}, \quad (5)$$

which is actually a correct result for $D \geq 0$ and $\mathbf{H}$ along the z axis. In this case one can easily choose vectors $\mathbf{S}_0$ and $\mathbf{S}_{\mathbf{Q}}$ in (5) that satisfy all N “strong” conditions (2) for any D , or for any direction of the field, if $D = 0$. Thus, according to the Luttinger-Tisza theorem, the resultant spin configuration is the solution of (3), *ie* it minimizes the energy (1) under the “strong” conditions (2).

Unfortunately, except for the above important but simple cases, simple solution obtained in this way appears to be physically meaningless. For example, for the negative (easy-axis) anisotropy, the $H = 0$ magnetic structure predicted with the help of the “weak” condition is a collinear configuration with spins of varying length, parallel to the z axis.⁴ This prediction, in particular, contradicts the experimental data in CsNiCl_3 and related compounds, where the easy-axis anisotropy is known to align the spin plane parallel to z -axis and to distort slightly the perfect 120° exchange structure, initially described by a spiral with $\mathbf{Q} = (\frac{1}{3}, \frac{1}{3}, 1)$, in reciprocal lattice units (rlu). In fact, the “incorrect” collinear phase, corresponding to

the longitudinal helimagnet, also appears in CsNiCl_3 , in the narrow temperature interval between the two T_N ¹⁸.

The reason for this contradiction and inconsistency of the trick with the “weak” condition is the following. It is easy to see, that by weakening the conditions on the spin length one may obtain additional minima that do not satisfy Eq. (2). These artifacts are thrown away by verifying all the conditions explicitly. However, some extrema of the initial problem (3) are also *lost* in this way. This can be visualized by considering the energy surface (1) in the space of spin components, cut through by the “physical” manifold (2). If the real solution, *ie* the global minimum, is one of the intersection points, it will be inevitably missed by employing the “weak” condition, since it is not an extremum of the function (1) in the extended space.

III. TRANSFORMATION TO THE LOCAL AXES

In order to perform the spin-wave calculation, one defines the local coordinate axes, $x_i y_i z_i$, such that classical spin at a site i points in z_i direction. The spin operators are then transformed to these axes and expanded into a series in Bose operators, *eg* using Holstein-Primakoff transformation. Because the local axis z_i is a classical equilibrium direction for spin at site i , the linear in spin deviations (*ie*, in operators $\hat{a}_i^+, \hat{a}_i$) terms are absent in the resultant boson Hamiltonian. Starting from this point, one can develop a slightly different procedure to find the classical ground state of the Hamiltonian (1) and its sub-

sequent decomposition into a series in Bose operators. First, we transform the spins from the crystallographic xyz frame to the local coordinate axes $x_i y_i z_i$. In general, this is achieved by two rotations: first, by an angle θ_i around the y axis, and then by an angle ϕ_i around the new x'_i axis, as shown in Fig. 1. In the resultant local frame the spin operators are

$$\tilde{S}_i = \|\mathbf{T}_{2,i}\| \cdot \|\mathbf{T}_{1,i}\| \cdot \mathbf{S}_i = \|\mathbf{T}_i\| \cdot \mathbf{S}_i, \quad (6)$$

where the transformation matrices are defined by

$$\begin{aligned} \|\mathbf{T}_{1,i}\| &= \begin{vmatrix} \cos \theta_i & 0 & -\sin \theta_i \\ 0 & 1 & 0 \\ \sin \theta_i & 0 & \cos \theta_i \end{vmatrix}, \\ \|\mathbf{T}_{2,i}\| &= \begin{vmatrix} 1 & 0 & 0 \\ 0 & \cos \phi_i & -\sin \phi_i \\ 0 & \sin \phi_i & \cos \phi_i \end{vmatrix}. \end{aligned} \quad (7)$$

The transformed Hamiltonian becomes,

$$\begin{aligned} \hat{\mathcal{H}} = \sum_{i,j} J_{ij} \tilde{S}_i \|\mathbf{T}_{ij}^{(\text{ex})}\| \tilde{S}_j + D \sum_i \tilde{S}_i \|\mathbf{T}_i^{(a)}\| \tilde{S}_i \\ - \gamma \mathbf{H} \sum_i \|\mathbf{T}_i\|^{-1} \tilde{S}_i. \end{aligned} \quad (8)$$

Here the matrices $\|\mathbf{T}_i^{(a)}\|$ and $\|\mathbf{T}_{ij}^{(\text{ex})}\|$, which define the bilinear in spin components forms coming from the anisotropy and the exchange coupling, respectively, are given by

$$\|\mathbf{T}_{ij}^{(a)}\| = \begin{vmatrix} \sin^2 \theta_i & \sin \phi_i \sin \theta_i \cos \theta_i & -\cos \phi_i \sin \theta_i \cos \theta_i \\ \sin \phi_i \sin \theta_i \cos \theta_i & \sin^2 \phi_i \cos^2 \theta_i & -\sin \phi_i \cos \phi_i \cos^2 \theta_i \\ -\cos \phi_i \sin \theta_i \cos \theta_i & -\sin \phi_i \cos \phi_i \cos^2 \theta_i & \cos^2 \phi_i \cos^2 \theta_i \end{vmatrix}, \quad (9)$$

and,

$$\|\mathbf{T}_{ij}^{(\text{ex})}\| = \begin{vmatrix} \cos \theta_{ij} & \sin \theta_{ij} \sin \phi_j & -\sin \theta_{ij} \cos \phi_j \\ -\sin \theta_{ij} \sin \phi_i & \cos \phi_i \cos \phi_j + \cos \theta_{ij} \sin \phi_i \sin \phi_j & \cos \phi_i \sin \phi_j - \cos \theta_{ij} \sin \phi_i \cos \phi_j \\ \sin \theta_{ij} \cos \phi_i & \sin \phi_i \cos \phi_j - \cos \theta_{ij} \cos \phi_i \sin \phi_j & \sin \phi_i \sin \phi_j + \cos \theta_{ij} \cos \phi_i \cos \phi_j \end{vmatrix}, \quad (10)$$

where $\theta_{ij} = \theta_i - \theta_j$. The angles θ_i and ϕ_i must be chosen so as to cancel the terms $\tilde{S}_i^x \tilde{S}_j^z$ and $\tilde{S}_i^y \tilde{S}_j^z$ which give rise

to the linear, in $\hat{a}_i^+, \hat{a}_i$, contribution to the Hamiltonian (8). This leads to the following system of $2N$ equations:

$$\begin{aligned} \sum_i 2J_{ij} \cos \phi_i \sin \theta_{ij} &= D \cos \phi_j \sin 2\theta_j + \tilde{\gamma} H_x \cos \theta_j - \tilde{\gamma} H_z \sin \theta_j, \\ \sum_i 2J_{ij} (\cos \phi_j \sin \phi_i - \sin \phi_j \cos \phi_i \cos \theta_{ij}) \\ &= D \sin 2\phi_j \cos^2 \theta_j - \tilde{\gamma} H_x \sin \phi_j \sin \theta_j + \tilde{\gamma} H_y \cos \phi_j - \tilde{\gamma} H_z \sin \phi_j \cos \theta_j, \end{aligned} \quad (11)$$

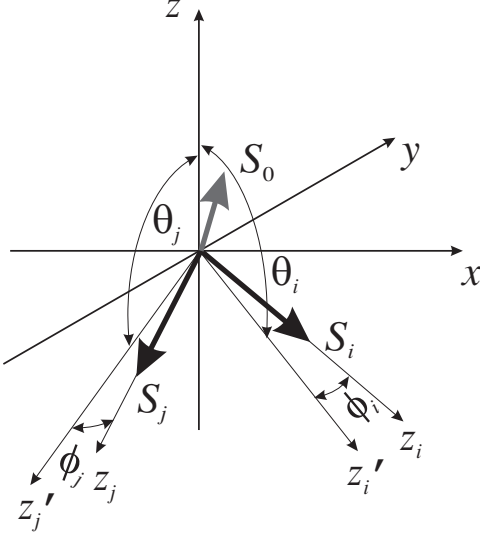


FIG. 1: Transformation to the local axes for the distorted exchange spiral.

where $\tilde{\gamma} = \gamma/S$. Evidently, this system for the angles θ_i and ϕ_i cannot be solved for arbitrary D and H . As it was mentioned above, only the cases $D = 0$ and $D > 0$, $\mathbf{H} \parallel z$ can be treated explicitly^{1,11}. However, we can start with the Heisenberg exchange Hamiltonian in a magnetic field

as a zero approximation and then look for the corrections, expanding them in powers of D . A very similar approach was developed by Andreev and Marchenko¹⁹ in the framework of the phenomenological Lagrangian theory. They found a rather simple and general solution of the problem in the leading order of perturbation.

IV. EASY-AXIS ANISOTROPY ($D < 0$)

First, we consider the more complicated case of the easy-axis anisotropy, which leads to the most general distortion of the exchange structure. Without the loss of generality we can set the magnetic field to lie in the yz plane. In this case the “right” unperturbed spiral should contain the z axis already at $H = 0$. Therefore, we look for the solution of Eq. (11) in the form,

$$\begin{cases} \theta_i = \mathbf{Q}\mathbf{r}_i + \delta\theta_i \\ \phi_i = \phi_0 + \delta\phi_i \end{cases}, \quad \sin \phi_0 = \frac{\tilde{\gamma}H}{2(J_0 - J_Q)}. \quad (12)$$

In most cases we will consider only the leading (*ie*, the lowest order in D) corrections $\delta\theta_i$, $\delta\phi_i$. Thus, substituting (12) into (11), it is sufficient to expand the trigonometric functions to the first order in $\delta\theta_i$, $\delta\phi_i$. As a result, we obtain the following equations for the deviations

$$\begin{aligned} \sum_i 2J_{ij} (\cos \phi_0 \cos(\mathbf{Q}\mathbf{r}_{ij}) \delta\theta_i - \sin \phi_0 \sin(\mathbf{Q}\mathbf{r}_{ij}) \delta\phi_i) \\ = 2J_Q \cos \phi_0 \delta\theta_j + D \cos \phi_0 \sin(2\mathbf{Q}\mathbf{r}_j) - \tilde{\gamma}H_z (\cos(\mathbf{Q}\mathbf{r}_j) \delta\theta_j + \sin(\mathbf{Q}\mathbf{r}_j)) , \\ \sum_i 2J_{ij} [(\cos^2 \phi_0 + \sin^2 \phi_0 \cos(\mathbf{Q}\mathbf{r}_{ij})) \delta\phi_i + \sin \phi_0 \cos \phi_0 \sin(\mathbf{Q}\mathbf{r}_{ij}) \delta\theta_i] \\ = 2(J_0 \sin^2 \phi_0 + J_Q \cos^2 \phi_0) \delta\phi_j + D \sin \phi_0 \cos \phi_0 (1 + \cos(2\mathbf{Q}\mathbf{r}_j)) \\ - (\tilde{\gamma}H_y \sin \phi_0 + \tilde{\gamma}H_z \cos \phi_0 \cos(\mathbf{Q}\mathbf{r}_j)) \delta\phi_j + \tilde{\gamma}H_z \sin \phi_0 \sin(\mathbf{Q}\mathbf{r}_j) \delta\theta_j \end{aligned} \quad (13)$$

which are rather easy to solve. Indeed, upon convolution with $J_{ij} \cos(\mathbf{Q}\mathbf{r}_{ij})$, the variations $\delta\theta_i$ and $\delta\phi_i$ should yield the trigonometric functions $\cos(\mathbf{Q}\mathbf{r}_j)$, $\sin(\mathbf{Q}\mathbf{r}_j)$, $\cos(2\mathbf{Q}\mathbf{r}_j)$, $\sin(2\mathbf{Q}\mathbf{r}_j)$, *etc*, which must cancel the right-hand side of the Eq. (11). Thus, they should be searched in the form of an expansion, $\delta\theta_i = \sum_n (\alpha_n \cos(n\mathbf{Q}\mathbf{r}_i) + \beta_n \sin(n\mathbf{Q}\mathbf{r}_i))$, where the order of the coefficients α_n , β_n is H^n and $|D|^{n/2}$.

An important remark is due here. One can also look for the solution of Eq. (11) with $\theta_i = \psi + \mathbf{Q}\mathbf{r}_i + \delta\theta_i$, instead of Eq. (12). It differs by rotation of the arbitrarily chosen “first” spin, and thus of the whole spin structure, by an angle ψ within the plane of the spiral. Evidently, in the leading approximation (to the first or-

der in D) all such structures have the same energy, as it was the case for the pure exchange. This fact reflects the remaining continuous degeneracy of the ground state with respect to such rotations. Moreover, by performing the corresponding expansions, it can be shown in a straightforward algebraic way that this degeneracy exists for all orders in H and $\sqrt{|D|}$ up to n which satisfies the condition $n\mathbf{Q} \equiv 0$, if such n exists. This condition means that spin structure is a commensurate spiral and can be described in terms of n sublattices. In this case the continuous degeneracy corresponding to spin rotations within the spiral plane is lifted in the order H^n and $|D|^{n/2}$. The ground state preserves only n -fold degeneracy corresponding to the arbitrary choice of the “first”

spin, *ie*, to the rotation of all spins in the exchange structure by an angle $(2\pi m)/n$ in the plane of the spiral. In the case of the incommensurate helimagnet, where this discrete symmetry is absent, the continuous degeneracy of the ground state is not lifted.

The above conclusions can be established from very general arguments. Evidently, a perturbation of the n -sublattice exchange spiral by adding $D \sum_i \cos^2(\psi + \theta_i)$ and $H \sum_i \cos(\psi + \theta_i)$ to the exchange Hamiltonian is invariant with respect to the transformation $\psi \rightarrow \psi + (2\pi m)/n$. Thus, the perturbed ground-state energy should not contain harmonics below $\cos(n\psi)$ and $\sin(n\psi)$. Hence, explicit dependence on the angle ψ in its Taylor expansion with respect to the perturbation parameters D and H only appears in the $n/2$ -th and n -th order terms, respectively. Another way to establish this fact is based on exchange symmetry arguments¹⁹. Exchange structure with n sublattices has an n -fold rotation axis perpendicular to the spin plane. Thus, the lowest-order perturbation of the exchange energy which has appropriate symmetry and which lifts such rotations must be proportional to $\cos(n\psi)$. In the case of the uniaxial anisotropy which already contains the two-fold symmetry, it is achieved in the $n/2$ -th order of perturbation. Magnetic field, on the other hand, can lift the n -fold rotation axis characteristic of exchange spiral only in the n -th order of perturbation. With the continuous GS degeneracy removed, the energy gap appears in the corresponding (formerly) Goldstone mode. This gap is induced by an “effective field” $\sim |D|^{n/2}$, or $\sim H^n$, and, therefore, is of the order $\sim |D|^{n/4}$, and $\sim H^{n/2}$, respectively.

This situation was closely studied in the hexagonal CsNiCl₃-type antiferromagnets, which are our reference in the present paper. It was shown, that in the easy-axis case the structure with $\psi = 0$, described by Eqs. (12), is stabilized by the anisotropy in the third order of perturbation, and that the magnon gap $\sim |D|^{3/2}$ appears.^{20,21} For the easy-plane antiferromagnetic spiral in the transverse field the situation is different (as we discuss later), and the structure with $\psi = \pi/2$ is realized.^{12,14} Below, we consider the solution (12), which is stabilized by the easy-axis anisotropy, $D < 0$, for two important orientations of the magnetic field.

A. Magnetic field perpendicular to z -axis

This field orientation gives rise to the most general distortion of the exchange spiral. Deviations of the angles satisfying (13) are found in the form

$$\begin{aligned} \delta\theta_i &= \vartheta \sin(2\mathbf{Q}\mathbf{r}_i), \quad \delta\phi_i = \frac{D}{2(J_0 - J_{\mathbf{Q}})} \text{tg}\phi_0 + \varphi \cos(2\mathbf{Q}\mathbf{r}_i), \\ \vartheta &= \frac{D}{J_{3\mathbf{Q}} - J_{\mathbf{Q}}} + \frac{D}{J_{2\mathbf{Q}} - J_{\mathbf{Q}}} \text{tg}^2\phi_0, \quad \varphi = \frac{D}{J_{2\mathbf{Q}} - J_{\mathbf{Q}}} \text{tg}\phi_0. \end{aligned} \quad (14)$$

Note, that according to these expressions, the anisotropy causes a small modulation of the spiral winding angle, $(\mathbf{Q}\mathbf{r}_i)$, which propagates as $2(\mathbf{Q}\mathbf{r}_i)$. This naturally results in appearance of the harmonics at wave-vectors $\pm 2\mathbf{Q}$ and $\pm 3\mathbf{Q}$ in the lattice Fourier transform of the ground-state spin arrangement, in agreement with the early results of Nagamiya *et al.*,³ and Cooper and Elliott.¹⁵ Another point to be mentioned here is that small variations (14), which are treated here in the linear approximation, actually contain terms which increase with the magnetic field (the most dramatic is the second term in ϑ , proportional to H^2). Therefore, although these expressions are valid up to very high fields, they fail near the spin-flip transition, at

$$\tilde{\gamma}H_s \sim 2(J_0 - J_{\mathbf{Q}}) \left(1 + \frac{D}{2(J_{2\mathbf{Q}} - J_{\mathbf{Q}})} \right).$$

In fact, this failure is indicative of a phase transition to a new spin arrangement of the “fan” type, that was considered in detail by Nagamiya *et al.*³ A simple way to study this transition and the behavior of the system in the vicinity of the spin-flip field H_s , is to expand the angles ϕ_i in small deviations from $\pi/2$. This approach was applied in Ref. 14, where the field-induced transitions in the easy-plane triangular antiferromagnet CsMnBr₃ were studied.

The classical ground-state energy corresponding to the spin arrangement of the global minimum found above can be easily calculated from Eqs. (7)–(10),

$$\begin{aligned} E_{GS} &= NS^2 \left(J_{\mathbf{Q}} + \frac{1}{2} D - (J_0 - J_{\mathbf{Q}} + \frac{1}{2} D) \sin^2 \phi_0 \right) \\ &= NS^2 \left(J_{\mathbf{Q}} + \frac{1}{2} D \right) - \frac{1}{2} N \chi_{\perp} (\gamma H)^2, \end{aligned} \quad (15)$$

where we have introduced the transverse spin susceptibility per site, as follows,

$$\begin{aligned} \chi_{\perp} &= \frac{1}{2(J_0 - J_{\mathbf{Q}}) - D} \\ &= \frac{1}{2(J_0 - J_{\mathbf{Q}})} \left(1 + \frac{D}{2(J_0 - J_{\mathbf{Q}})} \right) + O(D^2). \end{aligned} \quad (16)$$

Spin structures are usually studied in neutron scattering experiments, by measuring the intensities of the magnetic Bragg peaks. At each $\mathbf{k}$, these are proportional to the structure factor, *ie* the square of the absolute value of the corresponding Fourier transform of spin density, $\mathbf{S}_{\mathbf{k}}$, which, therefore, can be called a Bragg amplitude. Thus, for comparison with the experiment, it is important to calculate the nonzero Bragg amplitudes $\mathbf{S}_{\mathbf{k}}$ which result from the solution (14). Introducing the unit vectors $\mathbf{e}_x$

and $\mathbf{e}_y$ along the x and y axes, respectively, we obtain,

$$\begin{aligned} \mathbf{S}_0 &= \mathbf{e}_y S \sin \phi_0 \left(1 + \frac{D}{2(J_0 - J_Q)} \right) = \chi_{\perp}(\gamma \mathbf{H}), \\ \mathbf{S}_Q &= \frac{1}{2}(\mathbf{e}_z - i\mathbf{e}_x) S \cos \phi_0 \left(1 - \frac{D}{2(J_0 - J_Q)} \text{tg}^2 \phi_0 \right) \\ &\quad - (\mathbf{e}_z + i\mathbf{e}_x) S \cos \phi_0 \left(\frac{D}{4(J_3 Q - J_Q)} + \frac{D}{2(J_2 Q - J_Q)} \text{tg}^2 \phi_0 \right), \\ \mathbf{S}_{2Q} &= \mathbf{e}_y S \sin \phi_0 \frac{D}{2(J_2 Q - J_Q)}, \\ \mathbf{S}_{3Q} &= (\mathbf{e}_z - i\mathbf{e}_x) S \cos \phi_0 \frac{D}{4(J_3 Q - J_Q)}. \end{aligned} \quad (17)$$

In calculating the Bragg intensities, $I_{\mathbf{k}} \sim |\mathbf{S}_{\mathbf{k}}|^2$, one has to keep in mind that vectors $\mathbf{S}_Q$ and $\mathbf{S}_{3Q}$ have a nonzero imaginary part.

B. Magnetic field along z -axis; low fields

This case seems to be less complicated, since the distortion of the exchange spiral (5) occurs only at low fields, $H < H_c \sim \sqrt{|D|\bar{J}}$, and is such that it leaves the spins co-planar. This means that $\phi_i = 0$, and that the second equation in (11) and in (13) is automatically satisfied. The first equation is reduced to a rather simple relation, from which, to the leading order in D and H , the small deviations $\delta\theta_i$ are,

$$\begin{aligned} \delta\theta_i &= \vartheta \sin(2Q\mathbf{r}_i) + \eta \sin(Q\mathbf{r}_i), \\ \vartheta &= \frac{D}{J_3 Q - J_Q}, \quad \eta = -\frac{\tilde{\gamma} H}{J_0 + J_2 Q - 2J_Q}. \end{aligned} \quad (18)$$

It is clear from these expressions, that a leading order is insufficient for our approximation. To be consistent to the first order in the anisotropy constant D , one has to perform the expansions to the second order in $\eta \sim H \leq \sqrt{|D|\bar{J}}$. Such improved procedure leads to the following corrected expression for ϑ ,

$$\vartheta = \frac{D}{J_3 Q - J_Q} + \eta^2 \left(\frac{J_2 Q - J_Q}{J_3 Q - J_Q} - \frac{1}{4} \right). \quad (19)$$

The corresponding ground-state energy and the parallel susceptibility per spin are

$$\begin{aligned} E_{GS} &= N S^2 \left(J_Q + \frac{1}{2} D - \frac{(\tilde{\gamma} H)^2}{4(J_0 + J_2 Q - 2J_Q)} \right), \\ \chi_{\parallel} &= \frac{1}{2(J_0 + J_2 Q - 2J_Q)}, \end{aligned} \quad (20)$$

so that we can rewrite, $\eta = -2\chi_{\parallel}(\tilde{\gamma} H)$. The Bragg amplitudes are also easy to calculate,

$$\begin{aligned} \mathbf{S}_0 &= \mathbf{e}_z S \frac{\tilde{\gamma} H}{2(J_0 + J_2 Q - 2J_Q)} = \chi_{\parallel} \gamma \mathbf{H}, \\ \mathbf{S}_Q &= \frac{1}{2}(\mathbf{e}_z - i\mathbf{e}_x) S \left[1 - \frac{D + \eta^2(J_2 Q - J_Q)}{2(J_3 Q - J_Q)} \right] \\ &\quad + \frac{i}{2} \mathbf{e}_x S \left[\frac{1}{2} \eta^2 - \frac{D + \eta^2(J_2 Q - J_Q)}{J_3 Q - J_Q} \right], \\ \mathbf{S}_{2Q} &= -(\mathbf{e}_z - i\mathbf{e}_x) S \frac{\tilde{\gamma} H}{4(J_0 + J_2 Q - 2J_Q)} \\ &= -\frac{1}{2} \chi_{\parallel} \gamma H (\mathbf{e}_z - i\mathbf{e}_x), \\ \mathbf{S}_{3Q} &= (\mathbf{e}_z - i\mathbf{e}_x) S \frac{D + \eta^2(J_2 Q - J_Q)}{4(J_3 Q - J_Q)}. \end{aligned} \quad (21)$$

Actually, we can calculate the homogeneous component of the spin density, $\mathbf{S}_0$, (ie the magnetization) with better accuracy than in Eq. (21), to $\sim |D|^{3/2}$. To be completely consistent in this order, one should add to $\delta\theta_i$ terms like $\beta \sin(3Q\mathbf{r}_i)$, with $\beta \sim |D|^{3/2}$. However, retained in the first order, these terms would not contribute to $\mathbf{S}_0$. For our purpose it is therefore sufficient to take $\delta\theta_i$ in the form (18), and simply retain more terms in the subsequent expansions. In this way we obtain the following correction to $\mathbf{S}_0$,

$$\begin{aligned} \mathbf{S}_0 &= \chi_{\parallel} \gamma \mathbf{H} \left[1 - \chi_{\parallel} D \left(3 - 4 \frac{J_2 Q - J_Q}{J_3 Q - J_Q} \right) \right. \\ &\quad \left. + (4\tilde{\gamma} H)^2 \chi_{\parallel}^3 (J_2 Q - J_Q) \left(\frac{J_2 Q - J_Q}{J_3 Q - J_Q} - \frac{1}{2} \right) \right]. \end{aligned} \quad (22)$$

This expression includes the leading nonlinearity of the magnetization, which is often important for comparison with experiment.

C. Magnetic field along z -axis; high fields

This is the simplest and the best-known case. At some critical field, $H_c \sim \sqrt{|D|\bar{J}}$, a usual spin-flop transition takes place, and structure becomes the same as that of the magnetized exchange spiral, (5),

$$\begin{aligned} \mathbf{S}_{\mathbf{k}} &= \mathbf{e}_z S \sin \phi_0 \delta_{\mathbf{k},0} + (\mathbf{e}_x + i\mathbf{e}_y) S \cos \phi_0 \delta_{\mathbf{k},Q} \\ &\quad + (\mathbf{e}_x - i\mathbf{e}_y) S \cos \phi_0 \delta_{\mathbf{k},-Q}. \end{aligned} \quad (23)$$

In this case,

$$\begin{aligned} E_{GS} &= N S^2 \left(J_Q - \frac{(\tilde{\gamma} H)^2}{4(J_0 - J_Q + D)} \right), \\ \sin \phi_0 &= \frac{\tilde{\gamma} H}{2(J_0 - J_Q + D)}. \end{aligned} \quad (24)$$

These expressions hold up to a full saturation. The corresponding spin-flip field, H_s , is defined from the condition $\sin \phi_0 = 1$. Comparing the expressions (20) and (24) for the ground state energy, one obtains the following universal formula for the spin-flop field H_c ,

$$\tilde{\gamma}H_c = \sqrt{2|D|(J_0 - J_Q) \left(1 + \frac{J_0 - J_Q}{J_{2Q} - J_Q}\right)}. \quad (25)$$

V. EASY-PLANE ANISOTROPY ($D > 0$)

For the easy-plane Heisenberg helimagnet, spin reorientation in magnetic field reveals no new features in addition to those described in the previous section. All spin configurations occurring in this case have their exact analogs for the easy-axis helimagnet. Therefore, it is sufficient to establish the correspondence between the cases. The simplest case is that of magnetic field directed along the z axis. The spin arrangement in this case appears to be exactly the same as in Sec. 4.3, and is described by the same expressions, Eqs. (23) and (24). However, here we must keep in mind that constant D is now positive.

If the field is applied in the easy plane, *eg* along the x axis, the spin arrangement in low fields is similar to that

described in Sec. 4.2. This correspondence, however, is not as direct as the one above. Since all spins lie in the same plane, the solution of Eqs. (11) is obtained with $\theta_i = \pi/2$ and $\phi_i = \mathbf{Q}\mathbf{r}_i + \delta\phi_i$. The first equation is then automatically satisfied, while the second one, for ϕ_i , becomes exactly the same as equation for θ_i in the case of a small field along the z -axis in the easy-axis case, $D < 0$, $H \parallel z$, $H < H_c$, but with $D = 0$. Since now the symmetry breaking in the (easy) spin plane is different, we must consider two possible solutions.

A. First, we assume $\delta\phi_i = \eta \sin \mathbf{Q}\mathbf{r}_i + \vartheta \sin 2\mathbf{Q}\mathbf{r}_i$, which is exactly the same as considered in Sec. 4.2. In this case we find that η and ϑ are given by Eqs. (18) and (19), but with $D = 0$. It is clear from the transformation Eq. (7) that the resultant Fourier components of the spin density are given by the same expressions (21), only with $\mathbf{e}_x$ and $\mathbf{e}_z$ replaced by $\mathbf{e}_y$ and $\mathbf{e}_x$, respectively. Evidently, such solution can be stabilized by the magnetic field in the case of a nearly ferromagnetic helimagnet, where spins tend to align along the field direction.

B. Now consider the solution with $\delta\phi_i = \pi/2 + \eta \cos \mathbf{Q}\mathbf{r}_i - \vartheta \sin 2\mathbf{Q}\mathbf{r}_i$. Parameters η and ϑ are again given by Eqs. (18) and (19). As discussed above, in our approximation this solution is degenerate with the previous (**A**), and differs from it only by the phase multipliers in Bragg amplitudes,

$$\begin{aligned} S_0 &= \chi_{\parallel} \gamma \mathbf{H} \left[1 + (4\tilde{\gamma}H)^2 \chi_{\parallel}^3 (J_{2Q} - J_Q) \left(\frac{J_{2Q} - J_Q}{J_{3Q} - J_Q} - \frac{1}{2} \right) \right], \\ S_Q &= \frac{1}{2} (\mathbf{e}_y + i\mathbf{e}_x) S \left[1 - \eta^2 \frac{J_{2Q} - J_Q}{2(J_{3Q} - J_Q)} \right] - \frac{1}{2} \mathbf{e}_y S \eta^2 \left[\frac{1}{2} - \frac{J_{2Q} - J_Q}{J_{3Q} - J_Q} \right], \\ S_{2Q} &= (\mathbf{e}_x - i\mathbf{e}_y) S \frac{\tilde{\gamma}H}{4(J_0 + J_{2Q} - 2J_Q)} = \frac{1}{2} \chi_{\parallel} \gamma H (\mathbf{e}_x - i\mathbf{e}_y), \\ S_{3Q} &= -(\mathbf{e}_y + i\mathbf{e}_x) S \eta^2 \frac{J_{2Q} - J_Q}{4(J_{3Q} - J_Q)}. \end{aligned} \quad (26)$$

It was shown by Chubukov¹² for the case of a six-sublattice commensurate helimagnet CsMnBr_3 , that it is a type-**B** structure that is stabilized by magnetic field in the sixth order, $\sim H^6$. A non-zero frequency, corresponding to the magnon gap $\sim H^3$, appears in the magnetic resonance spectrum. Magnetic field favors this solution for an antiferromagnetic spiral because in this case it tends to align all spins perpendicular to its direction. In a general case of n -sublattice antiferromagnetic spiral, structure (26) is stabilized by the magnetic field in the n -th order, as we have discussed in Sec. 4.

Above the spin-flop transition which occurs for $\mathbf{H} \perp z$ and $D > 0$ at same H_c , given by (25), the spin structure

becomes exactly the same as that discussed in Sec. 4.1 (assuming $\mathbf{H} \parallel y$), and is described by the same expressions, but with $D > 0$.

VI. CONCLUSION

In this paper we presented a general perturbative treatment of the spin reorientation process for a weakly anisotropic spin spiral described by the classical Heisenberg spin Hamiltonian (1) in a magnetic field. The calculations were performed up to the first order in the anisotropy constant D . Previously, each particular case

of this general problem was treated individually, typically in the framework of the multi-sublattice model. Many examples of such approach are found in the literature devoted to calculating the spin reorientation in “triangular” antiferromagnets on hexagonal lattice.^{12,13,14} Apart from the loss of generality, in many important non-trivial cases such calculations are very difficult and lead to involved formulas which depend on a particular setup of the exchange couplings. As a result, in most cases neither the spin-waves spectrum, nor even the magnetic resonance frequencies, can be calculated in an explicit analytical form on the basis of the sublattice model. In contrast, the description presented here is quite general, and the results are rather simple. They provide a solid basis for spin-wave calculations and for the estimates of the spin-fluctuation contribution to the ground-state energy which can often be very important (even for selecting the correct ground state). Although here we calculated the spin configurations only for two principal orientations of the magnetic field, the derivation can be easily generalized for any field orientation. To this end, one must simply retain all relevant terms in Eqs. (11), (13), and admix the $\sin(\mathbf{Q}\mathbf{r}_i)$ and $\cos(\mathbf{Q}\mathbf{r}_i)$ rotations to the angle variations $\delta\phi_i$, $\delta\theta_i$. Thus, for example, some results reported in Ref. 14 can be obtained in a more general way.

As discussed above, one can treat the magnetic structures and the long-wavelength spin dynamics within the perturbation approach based on exchange approximation in the framework of the phenomenological macroscopic Lagrangian theory, as was proposed by Andreev and Marchenko.¹⁹ For the systems described by the Hamiltonian (1) the leading relativistic corrections are equivalent to our treatment of the anisotropy. The macroscopic

theory has the advantage of being less sensitive to the fluctuation effects (the mean-field ground state is chosen better, to partially account for the fluctuations). However, it also has two substantial disadvantages in comparison with the microscopic description presented here. First, it is not aimed at (and is not suitable for) calculating a microscopic spin-density distribution, or a spin-wave spectrum in the whole Brillouin zone. Therefore, the results cannot be directly compared with neutron scattering experiments which are the most sensitive and powerful tool for studying spin systems. Second, to reproduce the higher-order effects, such as nonlinear magnetization given by Eq. (22), macroscopic theory requires introducing additional phenomenological constants. It is clear, that microscopic theory which is developed here in the classical-spin approximation is far from being complete, and requires additional treatment of quantum corrections. This point, as well as calculation of the spin-wave spectra, are beyond the scope of this paper, and will be subjects of our further studies.

Acknowledgments

We wish to thank L.-P. Regnault, J. Villain, and A. F. Andreev for interesting discussions of the problem and for illuminating remarks. We also thank A. S. Borovik-Romanov, L. A. Prozorova, A. I. Smirnov, and S. S. Sosin for reading the manuscript and for useful comments. The work of I. A. Z. was supported by Grant M3K000 of the International Science Foundation. M. E. Zh. acknowledges financial support from the Japan Society for the Promotion of Science.

-
- ¹ A. Yoshimori, J. Phys. Soc. Jpn. **14**, 807 (1959).
 - ² J. Villain, J. Phys. Chem. Solids **11**, 303 (1959).
 - ³ T. Nagamiya, in *Solid State Physics*, edited by F. Seitz, D. Turnbull and H. Ehrenreich, Vol. 20, 305 (Academic Press, New York, 1967); T. Nagamiya, T. Nagata, and Y. Kitano, Progr. Theor. Phys. **27**, 1253 (1962).
 - ⁴ T. A. Kaplan, Phys. Rev. **124**, 329 (1961).
 - ⁵ D. H. Lyons and T. A. Kaplan, Phys. Rev. **120**, 1580 (1960).
 - ⁶ W. B. Yelon and D. E. Cox, Phys. Rev. B **6**, 204 (1972); Phys. Rev. B **7**, 2024 (1973).
 - ⁷ M. Eibschutz, R. C. Sherwood, F. S. L. Hsu, and D. E. Cox, AIP Conf. Proc. **17**, 864 (1972).
 - ⁸ I. A. Zaliznyak, Solid State Commun. **84**, 573 (1992).
 - ⁹ A. V. Chubukov, J. Phys. C **17**, L991 (1984).
 - ¹⁰ E. Rastelli, L. Reatto, and A. Tassi, J. Phys. C **18**, 353 (1985); **19**, 19933 (1986).
 - ¹¹ T. Ohyama and H. Shiba, J. Phys. Soc. Jpn. **62**, 3277 (1993); **63**, 3454 (1994).
 - ¹² A. V. Chubukov, J. Phys. C **21**, L441 (1988).
 - ¹³ H. Tanaka, S. Teraoka, E. Kakekashi, K. Iio, and K. Nagata, J. Phys. Soc. Jpn. **57**, 3979 (1988); H. Tanaka, Y. Kaahwa, T. Hasegawa, M. Igarashi, S. Teraoka, K. Iio, and K. Nagata, J. Phys. Soc. Jpn. **58**, 2930 (1989).
 - ¹⁴ S. I. Abarzhi, A. N. Bazhan, L. A. Prozorova, and I. A. Zaliznyak, J. Phys.: Condens. Matter **4**, 3307 (1992).
 - ¹⁵ B. R. Cooper, R. J. Elliott, S. J. Nettel, and H. Suhl, Phys. Rev. **127**, 57 (1962); B. R. Cooper and R. J. Elliott, Phys. Rev. **131**, 1043 (1963).
 - ¹⁶ I. E. Dzyaloshinsky, Zh. Eksp. Teor. Fiz. **47**, 992 (1964) [Sov. Phys. JETP **20**, 665 (1965)].
 - ¹⁷ Yu. A. Izumov, Usp. Fiz. Nauk **144**, 439 (1984) [Sov. Phys. Usp. **27**, 845 (1984)].
 - ¹⁸ X. Zhu and M. B. Walker, Phys. Rev. B **36**, 3830 (1987); M. L. Plumer, A. Caillé, and K. Hood, Phys. Rev. B **39**, 4489 (1989).
 - ¹⁹ A. F. Andreev and V. I. Marchenko, Usp. Fiz. Nauk **130**, 39 (1980) [Sov. Phys. Usp. **23**, 21 (1980)].
 - ²⁰ I. A. Zaliznyak, L. A. Prozorova, and A. V. Chubukov, J. Phys. Condens. Matter **1**, 4743 (1989).
 - ²¹ S. I. Abarzhi, M. E. Zhitomirsky, O. A. Petrenko, S. V. Petrov, and L. A. Prozorova, Zh. Eksp. Teor. Fiz. **104**, 3232 (1993) [JETP **77**, 521 (1993)].